

## Original Research

### Sealing ability of BC sealer and AH Plus- An invitro study

<sup>1</sup>Vishu Midha, <sup>2</sup>Vasu Midha, <sup>3</sup>Shubh Tandon,

<sup>1,2,3</sup>Private Practitioner, Chandigarh, India

#### ABSTRACT:

**Background:** A complete root canal filling is substantial for long-term success of endodontic treatment. The present study was conducted to compare sealing ability of BC sealer and AH Plus using SEM and micro-CT. **Materials & Methods:** All teeth were instrumented to a size of 40/06 using a crown-down technique. Irrigation was with 2 mL 2.5% NaOCl was employed. Canals were then dried with paper points and samples were randomly divided into two groups. Group I samples were filled with AH Plus Root Canal Sealer and group II samples were filled with EndoSequence BC Sealer. All specimens were scanned using micro-CT and then three from each group were randomly selected for SEM analysis. **Results:** The mean total ROI volume (mm<sup>3</sup>), object (Dentine) volume (mm<sup>3</sup>), volume of closed pores (mm<sup>3</sup>), surface of closed pores (mm<sup>2</sup>), volume of open pores (mm<sup>3</sup>) and open porosity (%) at apical third was 7.2 and 7.4, 1.52 and 1.41, 0.153 and 0.121, 0.235 and 0.182, 4.50 and 6.26 and 65.2 and 73.9 in group I and II respectively. At middle third, in group I was 7.3, 1.45, 0.361, 0.324, 6.12 and 70.5 and in group II was 7.9, 1.34, 0.409, 0.435, 6.87 and 84.2 respectively. At coronal third, in group I was 7.3, 1.36, 0.63, 0.631, 6.34 and 75.2 and in group II was 7.9, 1.31, 0.87, 0.772, 6.77 and 82.8 in group II respectively. A significant difference was observed in apical third (P< 0.05). **Conclusion:** Authors found that both the sealant found to be equally effective.

**Key words:** Root canal, Sealant, Endodontic

Received: 18 October, 2021

Accepted: 21 November, 2021

**Corresponding author:** Vishu Midha, Private Practitioner, Chandigarh, India

**This article may be cited as:** Midha V, Midha V, Tandon S. Sealing ability of BC sealer and AH Plus- An invitro study. J Adv Med Dent Scie Res 2021;9(12):96-100.

#### INTRODUCTION

The long-term success of endodontic therapies relies on complete filling after root canal obturation.<sup>1</sup> Microleakage is one of the significant causes for endodontic failure, which occurs due to poor contacts between the gutta-percha and the sealer, the sealer and the dentin, or through voids within the sealer. In general, the oral bacteria could contaminate the entire length of root canal within 30 days of obturation while endotoxins from Actinobacillus

actinomycetemcomitans could be observed in obturated root canals within 20 days.<sup>2,3</sup>

A complete root canal filling is substantial for long-term success of endodontic treatment. The obturation is classically performed using gutta-percha and different types of root canal sealers. The root canal sealers fill the gaps between gutta-percha cones and the dentine walls. Therefore, these materials should present adequate physical properties.<sup>4</sup>

Many types and brands of sealing cements are commercially available. They can be divided into the following types: eugenol-zinc-oxide-based cements,

calcium-hydroxide cements, glass ionomers, plastic resins and MTA-based cement.<sup>5</sup> The search for an endodontic sealer that fulfills the requirements for the ideal physicochemical and biologic properties continues even though many different root canal filling materials have been advocated through the years, such as AH Plus, Sealapex and Endomethasone-N. The EndoSequence BC sealer, also named the iRoot SP; has been introduced as an ideal premixed and injectable biomaterial in the clinical, exhibiting excellent radiopaque properties.<sup>6</sup> The present study was conducted to compare sealing ability of BC sealer and AH Plus using SEM and micro-CT.

#### MATERIALS & METHODS

The present study comprised of 40 recently extracted single-rooted, human mandibular premolars. The approval for the study was obtained from institutional ethical clearance and review committee.

All teeth were decontaminated in 5.25% sodium hypochlorite for 2 hours. Preoperative radiographs

were obtained in the mesiodistal and buccolingual directions to confirm the presence of a single unmanipulated root canal without root caries. All teeth were decoronated at the cemento-enamel junction, and each root was adjusted to about 12 mm in length. Subsequently, a #10 K-File was inserted into the root canal until the tip was at the apex. The working length was determined by subtracting 0.5 mm from this length.

All teeth were instrumented to a size of 40/06 using a crown-down technique. Irrigation was with 2 mL

2.5% NaOCl was employed. Canals were then dried with paper points and samples were randomly divided into two groups. Group I samples were filled with AH Plus Root Canal Sealer and group II samples were filled with EndoSequence BC Sealer. All specimens were scanned using micro-CT and then three from each group were randomly selected for SEM analysis. Results thus obtained were assessed statistically. P value less than 0.05 was considered significant.

**RESULTS**

**Table I Distribution of samples based on sealers**

Groups	Group I	Group II
Sealer	AH Plus root canal sealer	Endo Sequence BC Sealer
Number of tooth	20	20


Table I shows that each group comprised of 20 teeth.

**Table II Presence of micro pores in root canal system**


Sections	Groups	Total ROI Volume (mm3)	Object (Dentine) Volume (mm3)	Volume of Closed Pores (mm3)	Surface of Closed Pores (mm2)	Volume of Open Pores (mm3)	Open Porosity (%)	P value
Apical third	Group I	7.2	1.52	0.153	0.235	4.50	65.2	0.02
	Group II	7.4	1.41	0.121	0.182	6.26	73.9	
Middle third	Group I	7.3	1.45	0.361	0.324	6.12	70.5	0.08
	Group II	7.9	1.34	0.409	0.435	6.87	84.2	
Coronal third	Group I	7.3	1.36	0.63	0.631	6.34	75.2	0.09
	Group II	7.9	1.31	0.87	0.772	6.77	82.8	

Table II, graph Ia, b, c shows that mean total ROI volume (mm3), object (Dentine) volume (mm3), volume of closed pores (mm3), surface of closed pores (mm2), volume of open pores (mm3) and open porosity (%) at apical third was 7.2 and 7.4, 1.52 and 1.41, 0.153 and 0.121, 0.235 and 0.182, 4.50 and 6.26 and 65.2 and 73.9 in group I and II respectively. At middle third, in group I was 7.3, 1.45, 0.361, 0.324, 6.12 and 70.5 and in group II was 7.9, 1.34, 0.409, 0.435, 6.87 and 84.2 respectively. At coronal third, in group I was 7.3, 1.36, 0.63, 0.631, 6.34 and 75.2 and in group II was 7.9, 1.31, 0.87, 0.772, 6.77 and 82.8 in group II respectively. A significant difference was observed in apical third (P< 0.05).


**Graph I a**

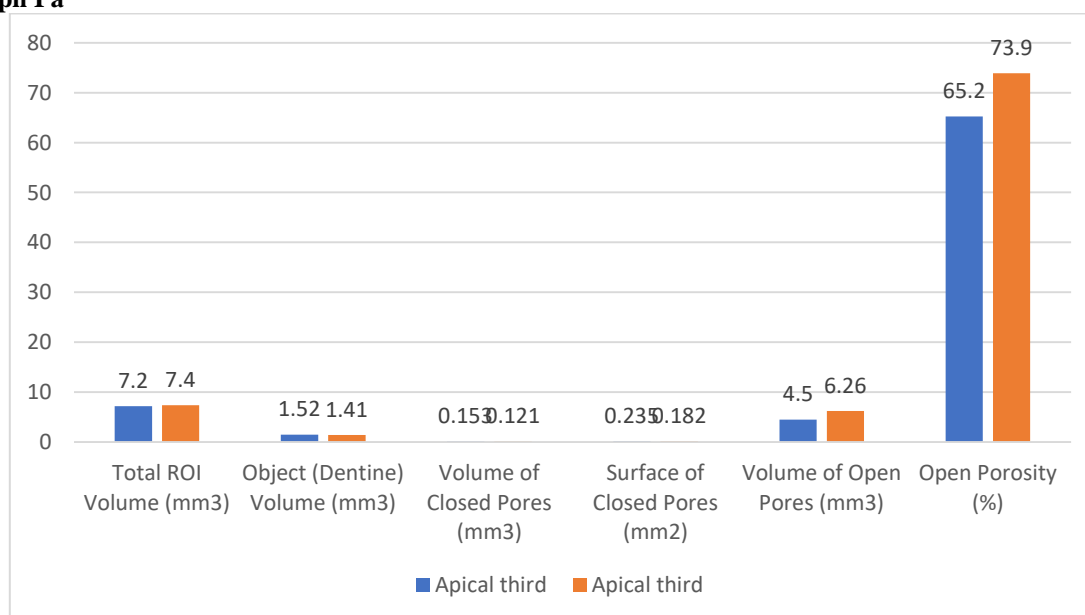

**Graph I b**

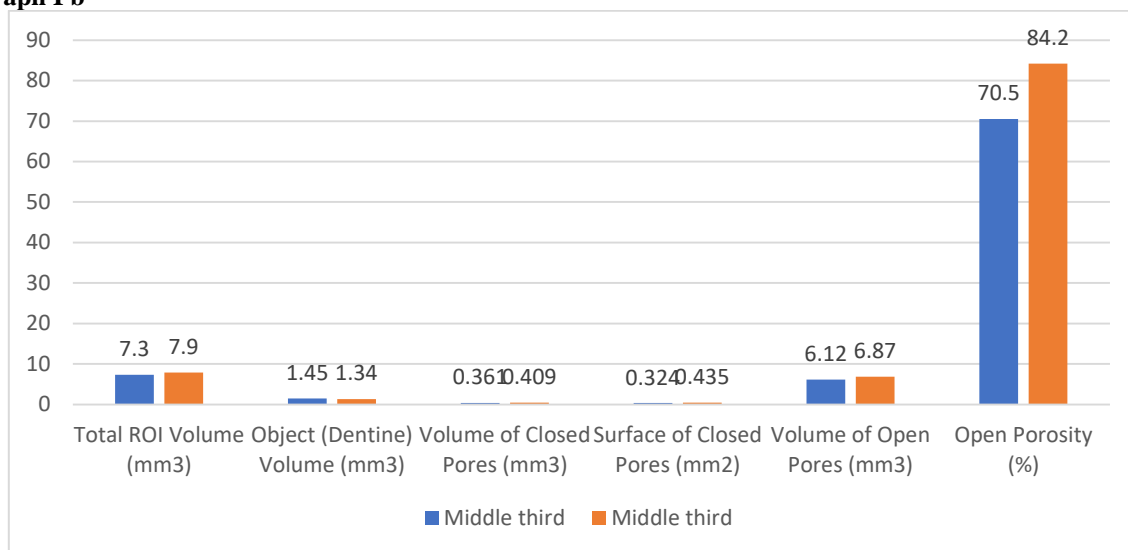

**Graph I c**

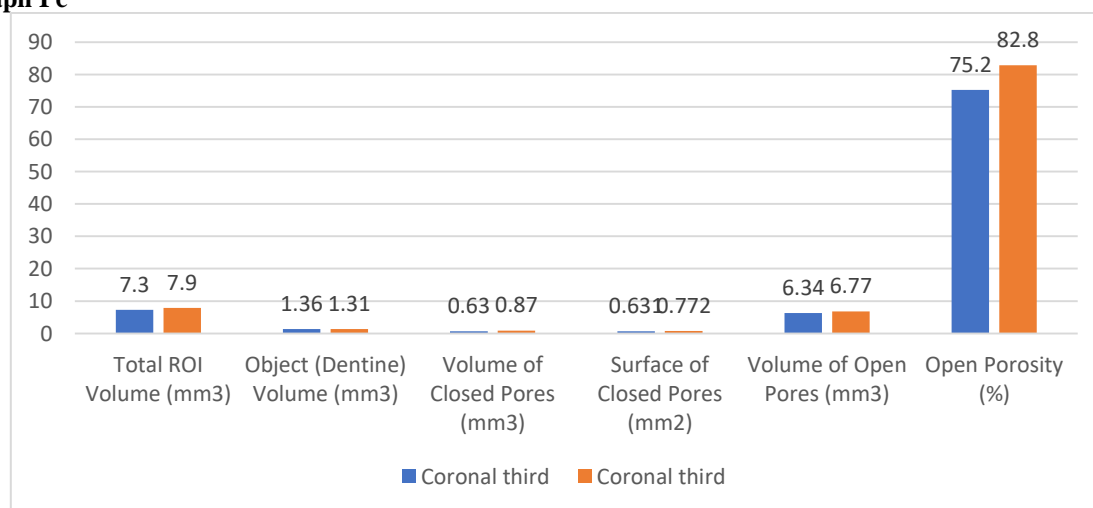

**DISCUSSION**

Due to the complexity of root canal systems, pulp tissue and inorganic debris remain in areas instruments and irrigation solutions cannot easily access after root canal treatments.<sup>7</sup> Thus, microorganisms surviving in the root canal will subsequently grow and spread to the periradicular areas between the sealer and dentin. Permanent coronal restorations also provide seals equally as important as the apical seal after the root canals are filled.<sup>8</sup> When insufficient coronal sealing occurs or the root canal remains open (e.g., when sealing is delayed for permanent fillings, broken fillings, or secondary caries formation; etc), oral bacteria will access the apical foramen.<sup>9</sup> A complete root canal filling is substantial for long-term success of endodontic treatment. The obturation is classically performed using gutta-percha and different types of root canal sealers. The root canal sealers fill the gaps between gutta-percha cones and the dentine walls. Therefore, these materials should present adequate physical properties.<sup>10</sup> Among the

important physical properties to a proper obturation, the flow of endodontic sealers allows their deeper penetrability into the irregularities of the root canal system, which contribute to own interlocking between sealer and dentine.<sup>11,12</sup> Therefore, the flow of endodontic sealers may be evaluated by the ISO 6876/2012 standard, which recommend that the materials have a minimum of 17 mm of flow. However, the main limitation of this conventional test is its incapability to evaluate also the filling ability of the materials.<sup>13</sup> The present study was conducted to compare sealing ability of BC sealer and AH Plus using SEM and micro-CT. In present study, group I samples were filled with AH plus root canal sealer and group II samples were filled with EndoSequence BC sealer. Huang et al<sup>14</sup> twenty-four single-root human mandibular premolars were selected and instrumented with nickel-titanium rotary file and the final file size was #40/06. They were then randomly allocated into 2 groups, and all samples were filled with single cone gutta-percha (#40/06) and one of the tested sealers (AH Plus and EndoSequence

BC sealers). All specimens were scanned using micro-CT and then three from each group were randomly selected for SEM analysis. According to SEM, both root canal sealers showed sufficient adaptation to dentin along the whole length of the root canal, though the coronal sections presented superior sealing than the apical sections. Micro porosity analyses revealed that the volume of closed pores and the surface of closed pores had the largest values in the coronal sections, followed by the middle and the apical sections for both sealants ( $p < 0.05$ ). However, no significant difference was observed for those two parameters between AH Plus and EndoSequence BC sealers in any of the three sections ( $p > 0.05$ ), whereas they were larger in the apical section when the AH Plus sealer was used. By using the single cone technique, neither EndoSequence or AH Plus provides a porosity-free root canal filling. The EndoSequence BC sealer may have similar sealing abilities regarding the whole root canal as the AH Plus sealer. A better sealing effect could be obtained in the coronal and middle sections of a root canal than the apical part by using the tested sealers.

We found that mean total ROI volume ( $\text{mm}^3$ ), object (Dentine) volume ( $\text{mm}^3$ ), volume of closed pores ( $\text{mm}^3$ ), surface of closed pores ( $\text{mm}^2$ ), volume of open pores ( $\text{mm}^3$ ) and open porosity (%) at apical third was 7.2 and 7.4, 1.52 and 1.41, 0.153 and 0.121, 0.235 and 0.182, 4.50 and 6.26 and 65.2 and 73.9 in group I and II respectively. At middle third, in group I was 7.3, 1.45, 0.361, 0.324, 6.12 and 70.5 and in group II was 7.9, 1.34, 0.409, 0.435, 6.87 and 84.2 respectively. At coronal third, in group I was 7.3, 1.36, 0.63, 0.631, 6.34 and 75.2 and in group II was 7.9, 1.31, 0.87, 0.772, 6.77 and 82.8 in group II respectively. Faria-Júnior et al<sup>15</sup> evaluated the flow rate of the Acroseal, AH Plus, Endomethasone N, Sealapex, and ActiV GP according to the standards of the ISO specification 6876/2001. A volume of 0.05 mL of the cement mixed according to the manufacturer's recommendations was placed on a glass plate. At  $180 \pm 5$  s after the commencement of mixing, the second glass plate was placed on top of the sealer, followed by the weight of mass approximately 100 g to make a total mass on the plate of  $120 \pm 2$  g. Ten min after the start of mixing, the weight was removed and the value of the diameter of the compressed disc of sealer was measured. The mean of three such determinations for each sealer was taken as the flow of the material. The results obtained were: Acroseal 21.24 mm, AH Plus 22.72 mm, ActiV GP 24.90 mm, Endomethasone N 18.76 mm, and Sealapex 25.15 mm. Conclusion: Only the Endomethasone N did not conform to ISO Specification that requires that a sealer shall have a diameter of not less than 20 mm. The Sealapex achieved the greatest flow, but it did not differ from Activ GP and AH Plus ( $P > 0.5$ ).

Torres et al<sup>16</sup> evaluated the flow and filling ability of AH Plus, Endofill and Sealapex by conventional

methodology and micro-CT. The flow of the sealers was analyzed according to ISO 6876/2012 and complemented by the area evaluation. Glass plates were manufactured with diameters of  $1 \times 1 \times 2$  mm and  $1 \times 1 \times 1$  mm (length, width and height), with a central cavity and four grooves in the horizontal and vertical directions. Each material was placed in the central cavity. Another glass plate and a metal weight were placed on the cement and kept for 10 minutes. The glass plate/sealer set was scanned using micro-CT. The flow was calculated by linear measurement of the material in the grooves. The central filling ( $\text{mm}^3$ ) was calculated in the central cavity and the lateral filling was measured up to 2 mm from the central cavity. All evaluated sealers presented flow according to ISO 6876 standards. The materials showed central cavity filling capacity higher than 80% and lateral filling greater than 75%. There was no difference in flow ( $\text{mm}$  and  $\text{mm}^2$ ) and in the filling ability ( $\text{mm}^3$ ) provided by the materials ( $p > 0.05$ ).

## CONCLUSION

Authors found that both the sealant found to be equally effective.

## REFERENCES

1. Al-Haddad A, Abu Kasim NH, Che Ab Aziz ZA. Interfacial adaptation and thickness of bioceramic-based root canal sealers. *Dent Mater J*. 2015;34(4):516–521.
2. Balguerie E, van der Sluis L, Vallaey K, Gurgel-Georgelin M, Diemer F. Sealer penetration and adaptation in the dentinal tubules: a scanning electron microscopic study. *J Endod*. 2011;37(11):1576–1579.
3. Barrieshi KM, Walton RE, Johnson WT, Drake DR. Coronal leakage of mixed anaerobic bacteria after obturation and post space preparation. *Oral Surg Oral Med Oral Pathol Oral Radiol Endod*. 1997;84(3):310–314.
4. Benenati FW. Obturation of the radicular space. In: Ingle JI, Bakland LK, Baumgartner JC, editors. *Ingle's Endodontics*. 6 ed. Hamilton: BC Decker; 2008. pp. 1053–1087.
5. Bouxsein ML, Boyd SK, Christiansen BA, Guldberg RE, Jepsen KJ, Müller R. Guidelines for assessment of bone microstructure in rodents using micro-computed tomography. *J Bone Miner Res*. 2010;25(7):1468–1486.
6. Brito-Júnior M, Santos LA, Faria-e-Silva AL, Pereira RD, Sousa-Neto MD. Ex vivo evaluation of artifacts mimicking fracture lines on cone-beam computed tomography produced by different root canal sealers. *Int Endod J*. 2014;47(1):26–31.
7. Çalt S, Serper A. Time-dependent effects of EDTA on dentin structures. *J Endod*. 2002;28(1):17–19.
8. Celikten B, Uzuntas CF, Orhan AI, Tufenkci P, Misirli M, Demiralp KO, et al. Micro-CT assessment of the sealing ability of three root canal filling techniques. *J Oral Sci*. 2015;57(4):361–366.
9. Ersahan S, Aydin C. Dislocation resistance of iRoot SP, a calcium silicate-based sealer, from radicular dentine. *J Endod*. 2010;36(12):2000–2002.

10. Ferrari M, Mannocci F, Vichi A, Cagidiaco MC, Mjör IA. Bonding to root canal: structural characteristics of the substrate. *Am J Dent*. 2000;13(5):255–260.
11. Gandolfi M, Parrilli A, Fini M, Prati C, Dummer PM. 3D micro-CT analysis of the interface voids associated with Thermafil root fillings used with AH Plus or a flowable MTA sealer. *Int Endod J*. 2013;46(3):253–263. [PubMed] [Google Scholar]
12. Gomes-Filho JE, Moreira JV, Watanabe S, Lodi CS, Cintra LT, Dezan E, Junior, et al. Sealability of MTA and calcium hydroxide-containing sealers. *J Appl Oral Sci*. 2012;20(3):347–351. [PMC free article] [PubMed] [Google Scholar]
13. Hammad M, Qualtrough A, Silikas N. Evaluation of root canal obturation: a three-dimensional in vitro study. *J Endod*. 2009;35(4):541–544.
14. Huang Y, Orhan K, Celikten B, Orhan AI, Tufenkci P, Sevimay S. Evaluation of the sealing ability of different root canal sealers: a combined SEM and micro-CT study. *Journal of Applied Oral Science*. 2018 Jan 15;26.
15. Faria-Júnior NB, Massi S, Croti HR, Gutierrez JC, Dametto FR, Vaz LG. Comparative assessment of the flow rate of root canal sealers. *Revista Odonto Ciência*. 2010;25:170-3.
16. TORRES FF, GUERREIRO-TANOMARU JM, PINTO JC, BONETTI-FILHO I, TANOMARU-FILHO M. Evaluation of flow and filling of root canal sealers using different methodologies. *Revista de Odontologia da UNESP*. 2020 Feb 10;48.